



**HAL**  
open science

## Fundamentals on corrosion and stress corrosion cracking

D. Feron, C. Guerre, D. Gomez Briceno

► **To cite this version:**

D. Feron, C. Guerre, D. Gomez Briceno. Fundamentals on corrosion and stress corrosion cracking. SOTERIA training School, Sep 2018, Valencia, Spain. cea-02338601

**HAL Id: cea-02338601**

**<https://cea.hal.science/cea-02338601>**

Submitted on 21 Feb 2020

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# FUNDAMENTALS ON CORROSION AND STRESS CORROSION CRACKING

Damien Féron\*, Catherine Guerre\* & Dolores Gomez Briceno\*\*

\* Den-SERVICE de la Corrosion et du Comportement des Matériaux dans leur Environnement (SCCME), CEA, Université Paris-Saclay, F-91191 Gif-sur-Yvette, France

\*\* Structural Materials Division, CIEMAT, 28040 Madrid, Spain



This project received funding under the Euratom research and training programme 2014-2018 under grant agreement N° 661913

1

## CONTENT

- ❑ Why corrosion?
  - Definition (ISO 8044)
  - Thermodynamics / Pourbaix diagrams
  - Kinetics stability diagrams
- ❑ Electrochemistry and water corrosion
  - Anodic and cathodic reactions
  - Current-potential curves
- ❑ Localised corrosion: Stress corrosion cracking
  - Phenomena
  - Key parameters
  - Historical background
- ❑ References


## Corrosion (ISO 8044, April 2000)

“Physicochemical interaction between a metal and its environment that results in changes in the properties of the metal, and which may lead to significant impairment of the function of the metal, the environment, or the technical system, of which these form a part.

- NOTE This interaction is often of an electrochemical nature.”



Minneapolis, USA, 2007

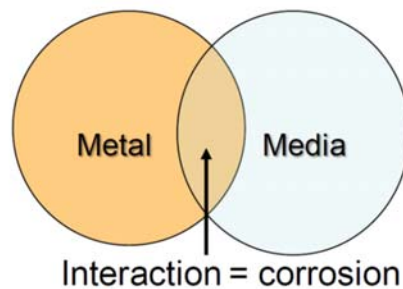

06/02/2019

SOTERIA

3

# Why Corrosion ?

- ❑ Industrial alloys are not thermodynamically stable in their environment
- ❑ Thermodynamic stability diagrams
- ❑ In water : E-pH diagrams
- ❑ Marcel Pourbaix, « Atlas d'équilibres électrochimiques », Gauthier-Villars, Paris, 1963


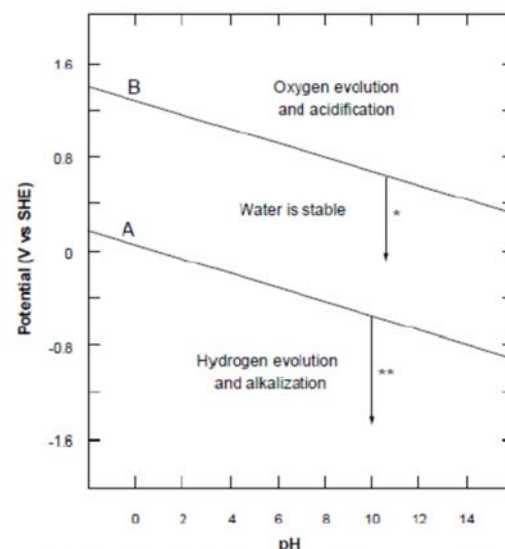


Figure 13 Thermodynamic stability of water, oxygen, and hydrogen. (A is the equilibrium line for the reaction:  $H_2 = 2H^+ + 2e^-$ . B is the equilibrium line for the reaction:  $2H_2O = O_2 + 4H^+ + 4e^-$ . \* indicates increasing thermodynamic driving force for cathodic oxygen reduction, as the potential falls below line B. \*\* indicates increasing thermodynamic driving force for cathodic hydrogen evolution, as the potential falls below line A.)

## Potential-pH diagrams / "Pourbaix diagrams"

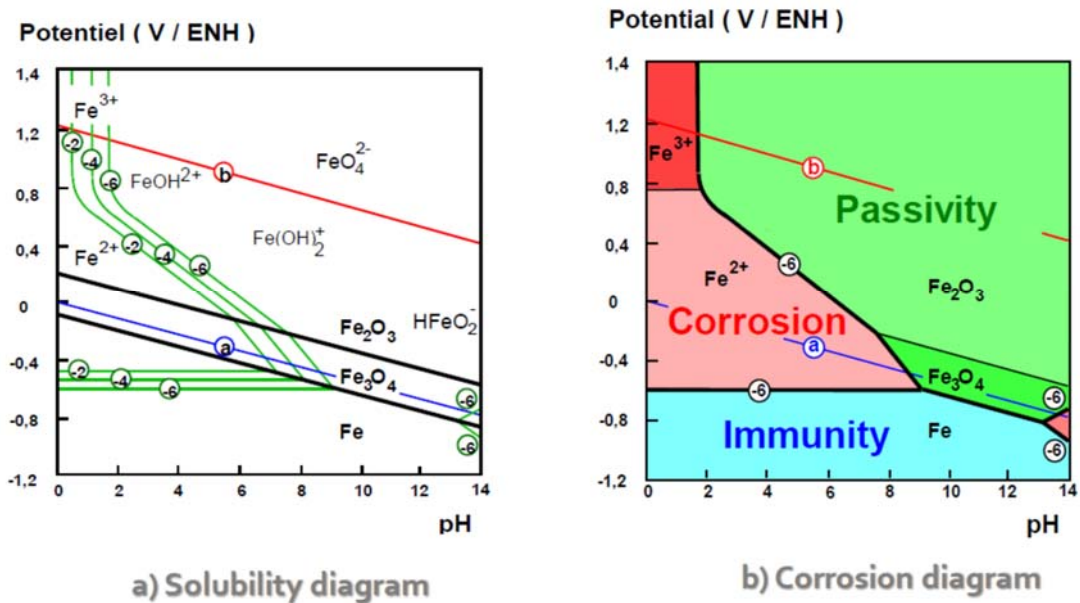


06/02/2019

SOTERIA Training School - September 2018 - Polytechnic University of Valencia

5

Regions of potential - pH diagram where different modes of Stress Corrosion Cracking occur for Alloy 600 at (300°C)

- ❑ LPSCC: low potential SCC
- ❑ HPSCC: high potential SCC
- ❑ AKSCC: Alkaline SCC
- ❑ AcSCC: Acid SCC
- ❑ AKIGC: Alkaline IGC
- ❑ Pb SCC: lead SCC
- ❑ Sy- SCC: Sulfur SCC

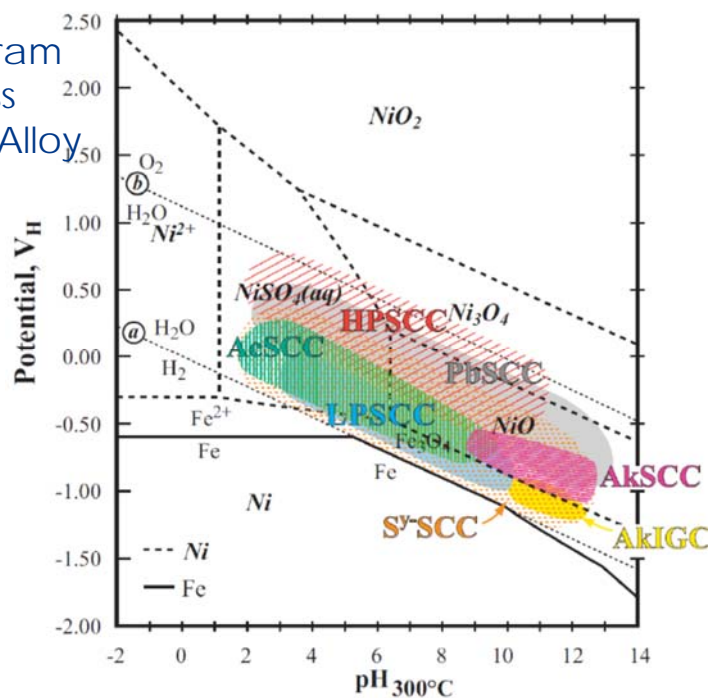


from Roger Staehle

06/02/2019

SOTERIA

6

## Thermodynamics # Kinetics

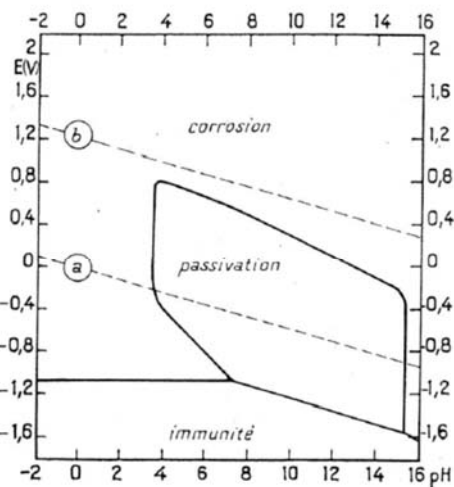a. Figure établie en considérant  $\text{Cr}(\text{OH})_2$ .

Chromium Pourbaix diagram

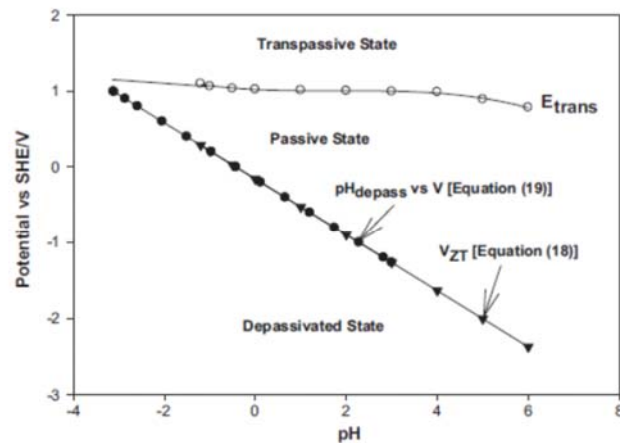


Fig. 9. Primitive Kinetic Stability Diagram (KSD) for Alloy X in 6.256 m NaCl at 50 °C.

Kinetic stability diagram (KSD)  
Chromium oxide passive layer  
(Digby MacDonald)

06/02/2019



SOTERIA

7


## CONTENT

- ❑ *Why corrosion?*
  - *Definition (ISO 8044)*
  - *Thermodynamics / Pourbaix diagrams*
  - *Kinetics stability diagrams*
- ❑ **Electrochemistry and water corrosion**
  - Anodic and cathodic reactions
  - Current-potential curves
  - Passivation
- ❑ **Localised corrosion: Stress corrosion cracking**
  - Phenomena
  - Key parameters
  - Initiation
  - Propagation
- ❑ **References**

**Electrochemical corrosion:** "corrosion involving at least one anodic reaction and one cathodic reaction"

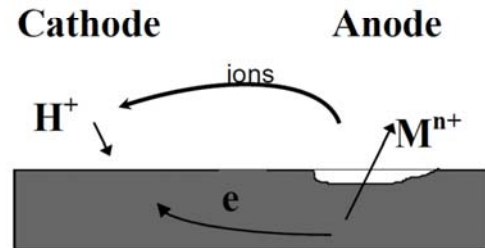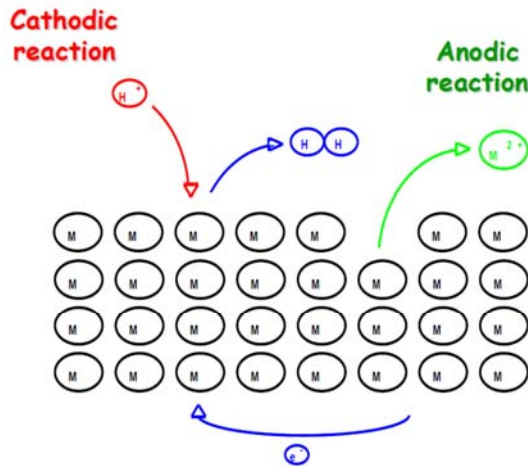


Aqueous corrosion (corrosion in LWRs) is an electrochemical corrosion


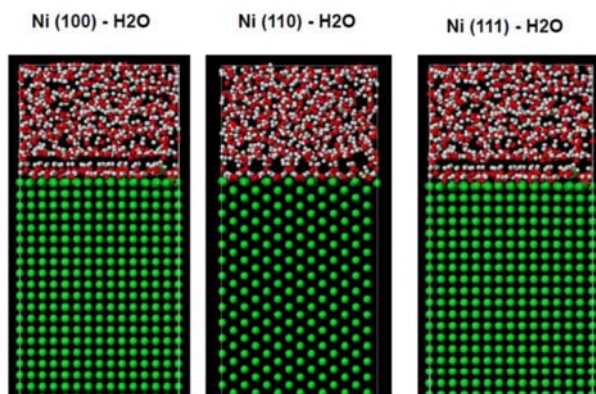


From B. Diawara & Al., 2012-2014

Molecular dynamics

- Surface reactivities
- Continuous oxide layer
- Hydrogen in the metal

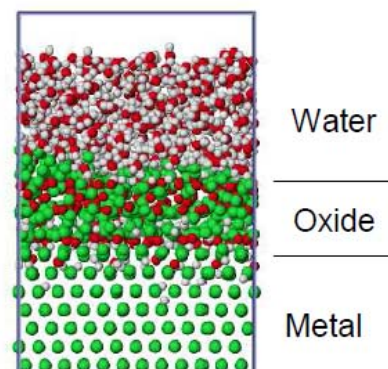

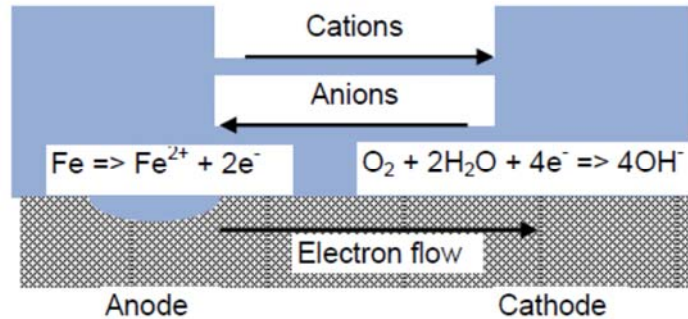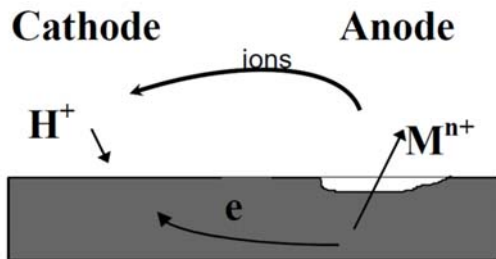

□ Main cathodic reactions in aqueous media

- $2\text{H}^+ + 2\text{e}^- \rightarrow \text{H}_2$  (acid environment – fast)
- $\text{O}_2 + 2\text{H}_2\text{O} + 4\text{e}^- \rightarrow 4\text{OH}^-$
- $\text{H}_2\text{O} + 2\text{e}^- \rightarrow \text{H}_2 + 2\text{OH}^-$  (slow – idem first one)



$$\text{Mass loss} = \frac{I \times t \times M}{z \times F}$$

$I$  is the current,  $t$  is the time,  $M$  is the molar mass of the metal,  $z$  is the number of electrons involved in the reaction and  $F$  is Faraday's constant.



# Anodic & cathodic curves

□ Anodic current is positive / Cathodic current is negative

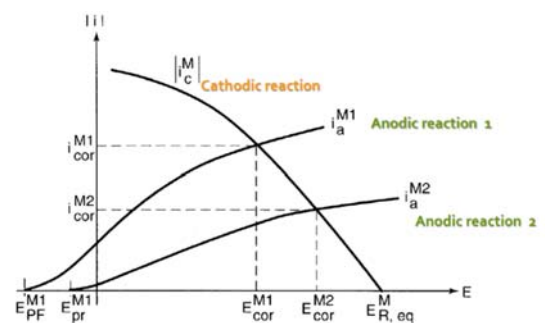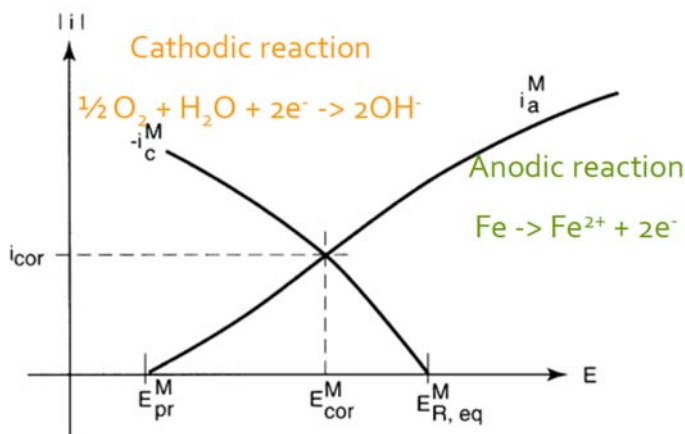

If the cathodic reaction rate is constant, free corrosion potential decreases when corrosion rate increase





**Passivation:** "decrease of corrosion rate by a passivation layer"

NOTE Incomplete passivation may lead to localized corrosion"

**Passivation layer:** "passive layer thin, adherent, protective layer formed on a metal surface through reaction between metal and environment"

## Anodic curves of a passive material

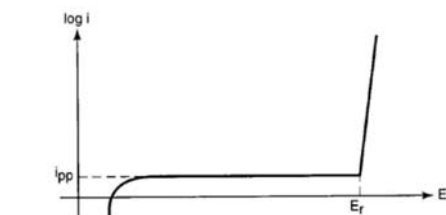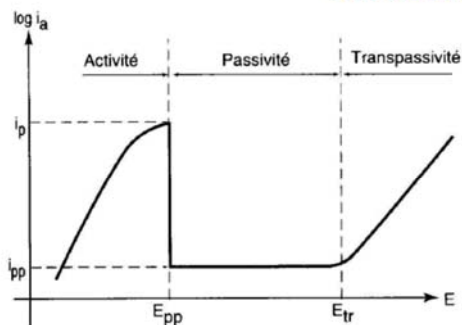

In neutral media, no activation peak



06/02/2019

SOTERIA

13

# CONTENT

- ❑ *Why corrosion?*
  - *Definition (ISO 8044)*
  - *Thermodynamics / Pourbaix diagrams*
  - *Kinetics stability diagrams*
- ❑ *Electrochemistry and water corrosion*
  - *Anodic and cathodic reactions*
  - *Current-potential curves*
  - *Passivation*
- ❑ *Localised corrosion: Stress corrosion cracking*
  - *Phenomena*
  - *Key parameters*
  - *Initiation*
  - *Propagation*
- ❑ *References*



06/02/2019

SOTERIA Training School - September 2018 - Polytechnic University of Valencia

14






- ❑ Environmental Assisted Cracking (EAC) covers different degradation modes
  - Stress corrosion cracking (SCC): cracking of a metal under the combined effects of constant stress and a specific environment
  - Corrosion fatigue (CF) takes place under cyclic stresses
  - Strain induced corrosion cracking (SICC): cracking under increasing strain
  
- ❑ Materials susceptible to SCC in LWR conditions
  - Austenitic stainless steels (300 type)
  - Nickel base alloys (Alloy 600, weld Alloys 82 & 182, Alloy X-750)
  - Low alloy & carbon steels
  - others



# SCC and alloys

- ❑ Main alloys in LWRs

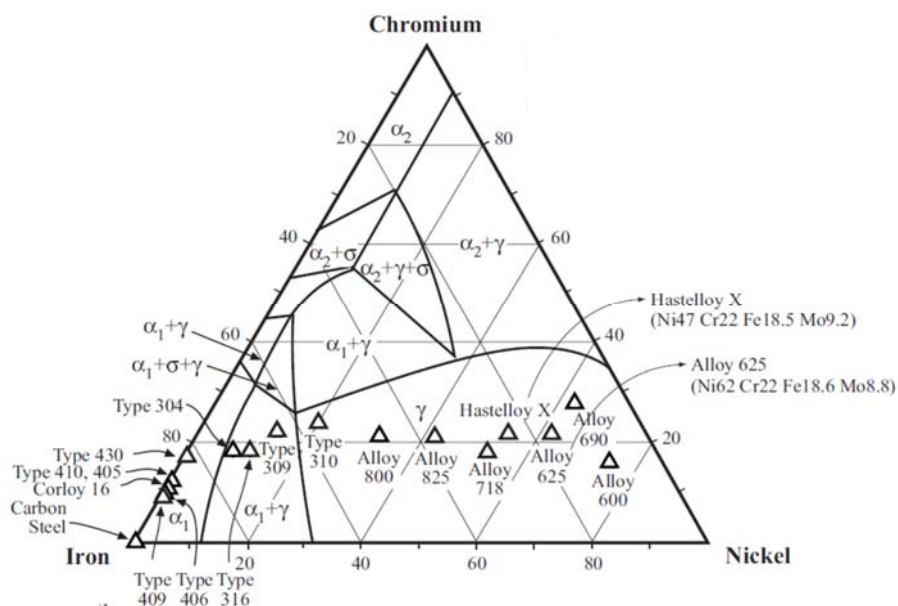


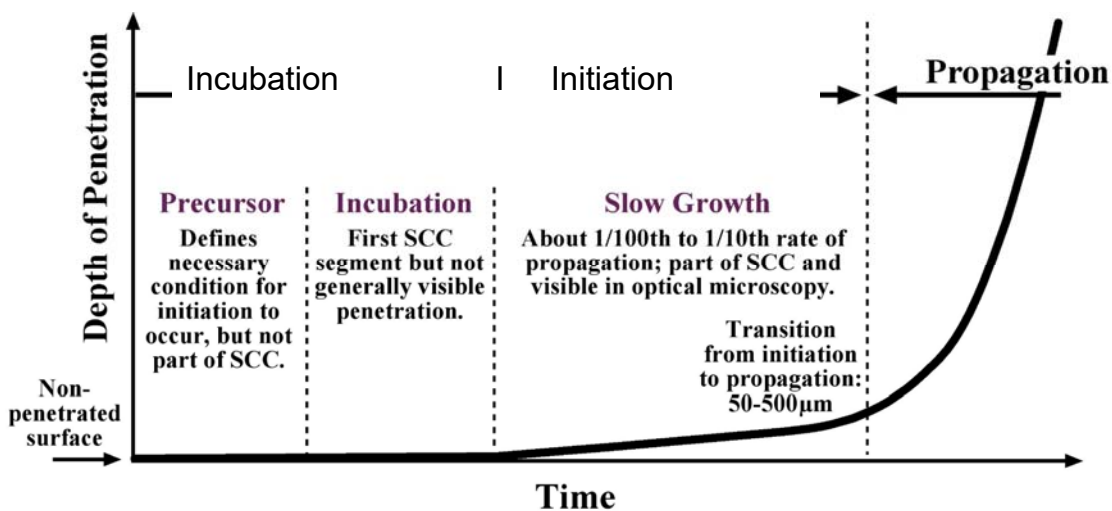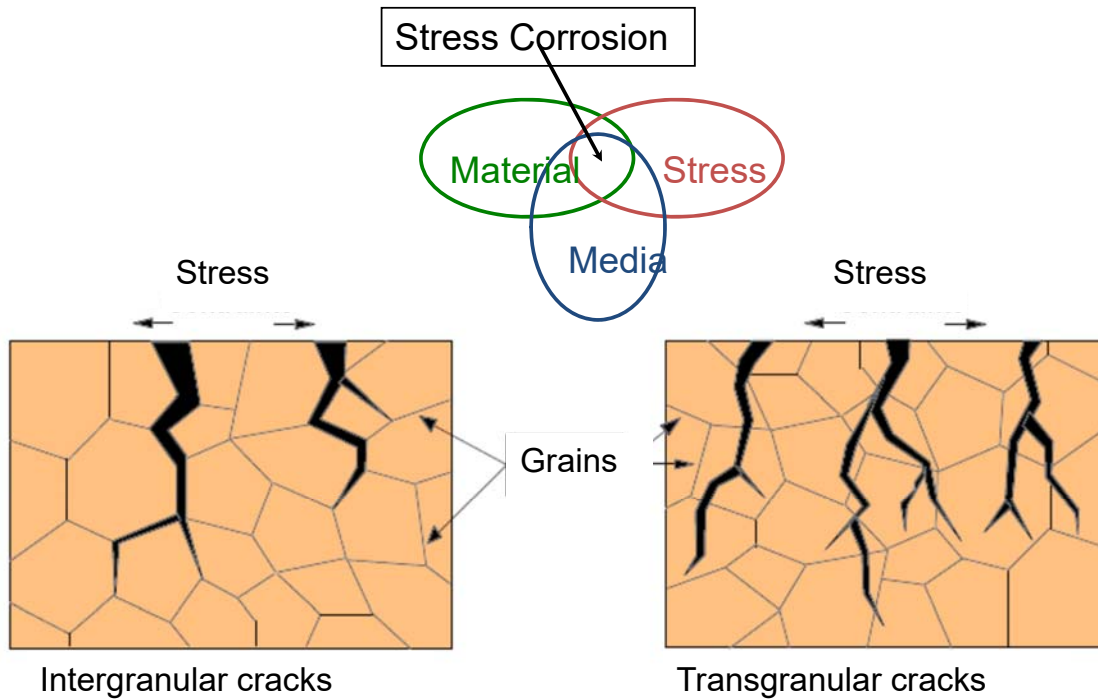


**Incubation:** Passive film formation and evolution

**Initiation:** Film rupture & Intergranular oxidation

**Propagation:** Internal oxidation & Hydrogen

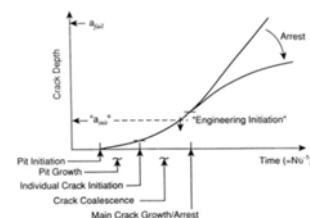

- Long initiation time

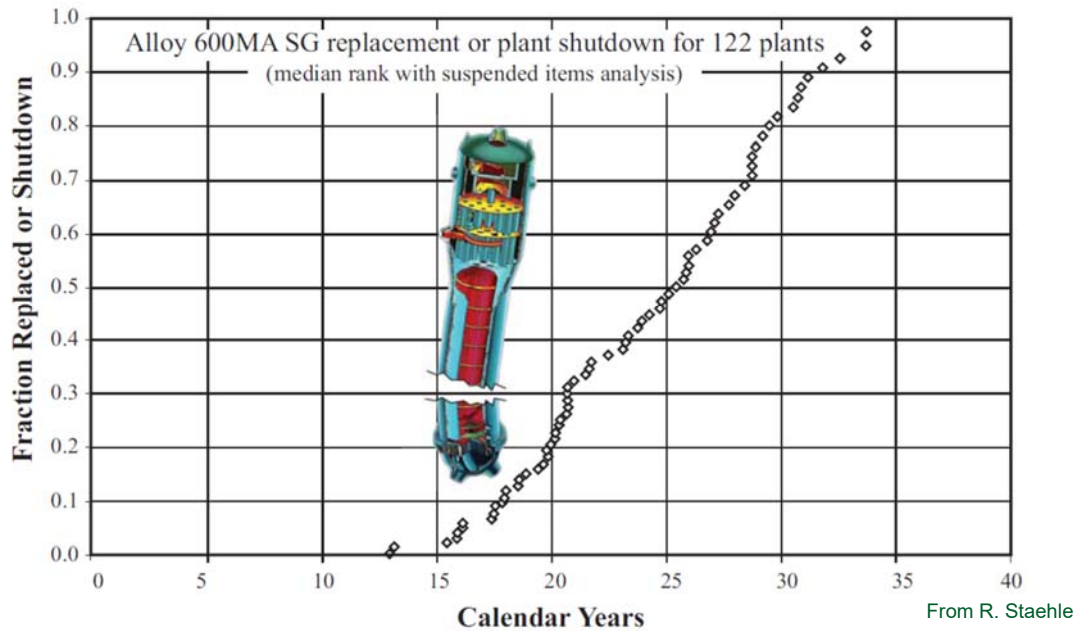


06/02/2019

SOTERIA

19

## SCC Key Parameters

- The complexity of SCC is reflected in the large number of influential variables (from Peter L. Andresen)

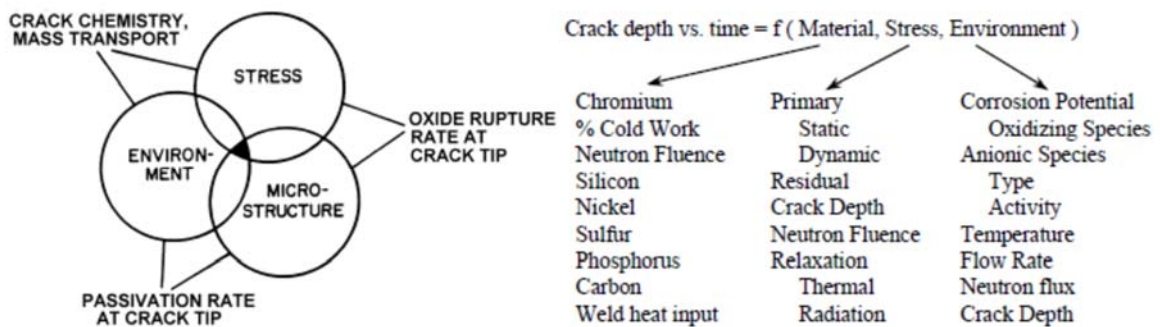

06/02/2019

SOTERIA


20

# SCC main parameters


From T. Yonezawa

Eight principal variables (from R. Staehle)

- Temperature
- Stress
- Alloy composition
- Alloy structure (cold work)
- Electrochemical potential
- Species (pollutants)
- pH
- Irradiation

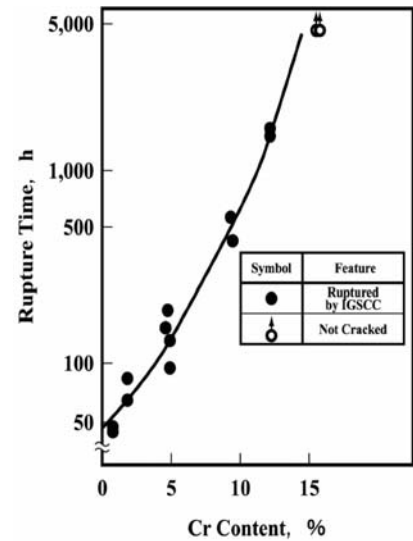

Influence of the alloy composition: 10% Fe-Cr-Ni alloys with various Cr contents

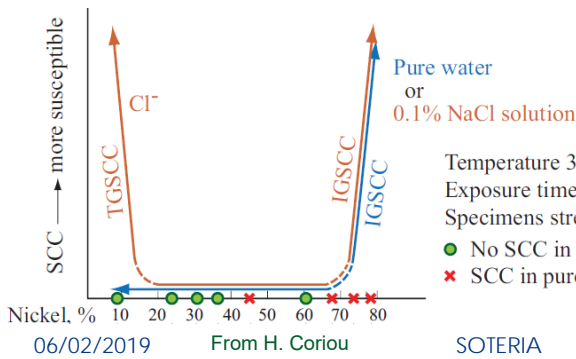

Influence of the alloy composition: Fe-18%Cr-Ni alloys with various Ni contents



06/02/2019


From H. Coriou

SOTERIA

21


# SCC and corrosion potential

Stainless steels

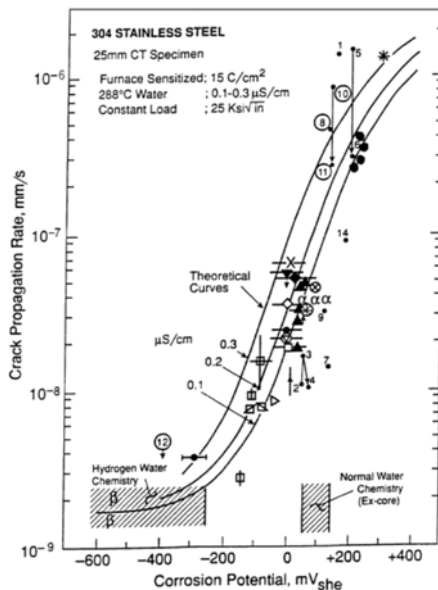

From P. Andresen

Nickel base alloy


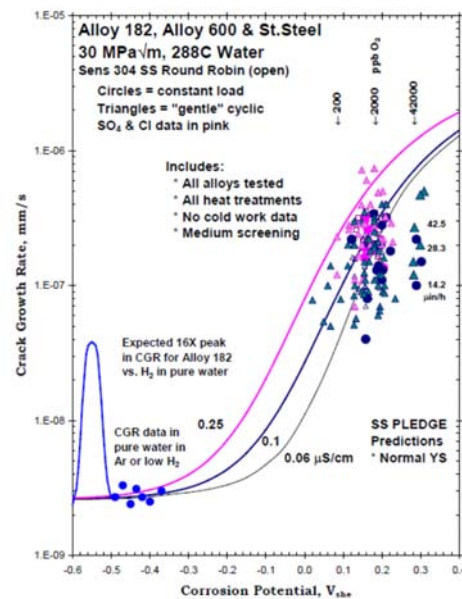


06/02/2019

SOTERIA

22

## □ Influence of temperature

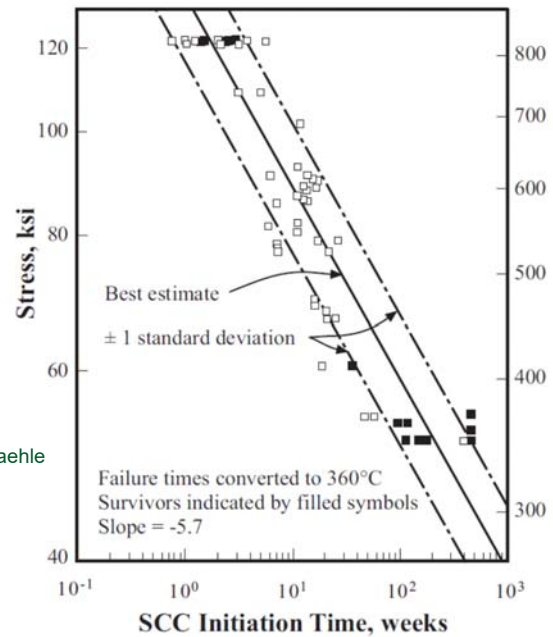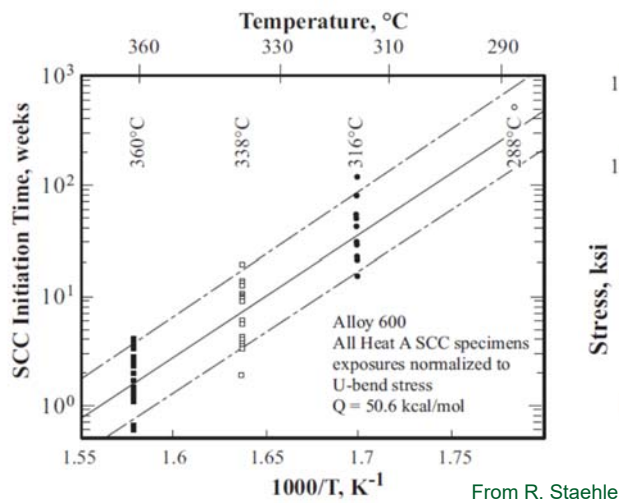


## □ Influence of stress




# Historical background - BWRs

*Austenitic stainless steels and nickel base alloys are susceptible to IGSCC in BWR conditions*

- ✓ Stainless Steels Fuel Cladding Late 1950s and Early 1960s
- ✓ 304 during Construction Late 1960s
- ✓ Furnace Sensitized Type 304 during Operation Late 1960s
- ✓ Welded Small Diameter Stainless Steel Piping Mid 1970s
- ✓ Large Diameter 304 Piping Late 1970s
- ✓ Alloy X750 Jet Pump Beam Late 1970s
- ✓ Alloy 182/600 in Creviced Nozzles w/sulfate Late 1970s
- ✓ Crevice-induced Cracking of Type 304L/316L Mid 1980s
- ✓ Localized Cold Work Initiates IGSCC in Resistant Material 1980s

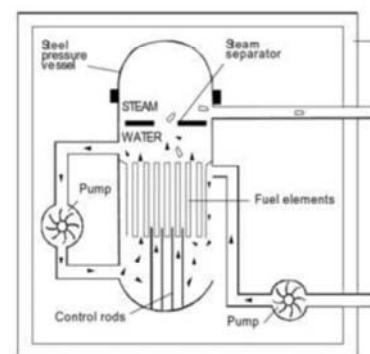

# SCC of Alloy 600 in PWRs or the « Coriou effect »

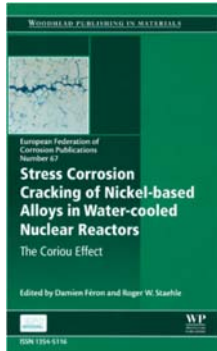

- ✓1957: Copson et al. (Inco, USA) proposed Alloy 600 (resistant to SCC cracking in boiling  $MgCl_2$ )
- ✓1959: *Coriou et al.* published that Alloy 600 is susceptible to SCC in pure water at 350°C.
- ✓1959-1975: Controversy between laboratory results in US and in France
- ✓1975-1985: Confirmation of the phenomena in pure water and in PWR primary water, named also "PWSCC" for Pure *or Primary* Water Stress Corrosion Cracking".
- ✓1985 – 1990s: generic phenomena occurring on Alloy 600 components and particularly on SG tubes.
- ✓1991 (in France) – 2002 (US, then Japan ...): cracking of vessel head penetrations (Alloy 600 tubes, Weld made of Alloy 18 or 82).



06/02/2019


SOTERIA

25

## To conclude



### ❑ Corrosion accuracy

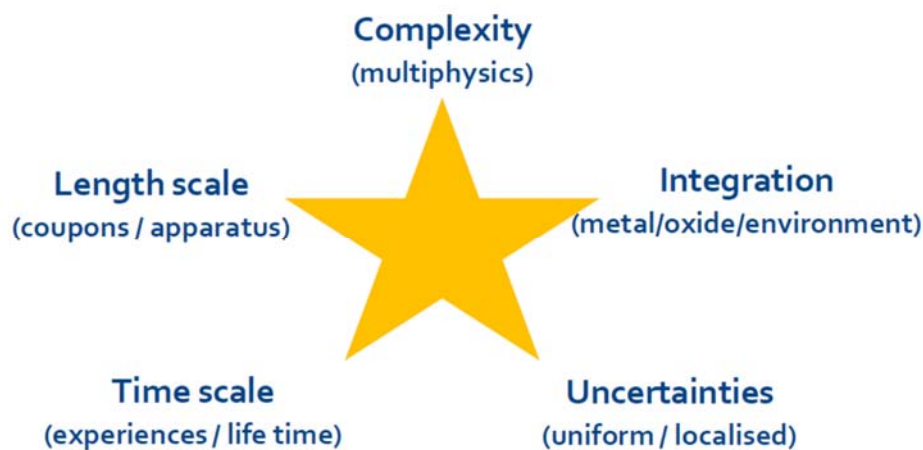

06/02/2019

SOTERIA

26

- ❑ P.L. Andresen, "SCC testing and data quality considerations" ,Ninth International Symposium on Environmental Degradation in Nuclear Power Systems –Water Reactors, TMS 1999.
- ❑ "Chemistry and Electrochemistry of Corrosion and Stress Corrosion Cracking: A symposium Honoring the Contribution of R.W. Staehle" ,TMS 2001.
- ❑ F.P. Ford, P.L. Andresen, " Corrosion in Nuclear Systems: Environmentally Assisted Cracking in Light Water Reactors" , in Corrosion Mechanisms in Theory and Practice, Marcel Deker, 2002.
- ❑ D. Féron & J.-M. Olive, Corrosion issues in light water reactors – Stress corrosion cracking, EFC N°51, Woodhead publishing, Cambridge, UK, 2007
- ❑ R A Cottis, M J Graham, R Lindsay, S B Lyon, SHREIR'S CORROSION, Elsevier, Oxford, 2010
- ❑ P. Marcus, 2011, Corrosion mechanism in theory and practice, third edition, Wiley, Frankfort, Germany
- ❑ D. Féron, « Nuclear Corrosion Science and Engineering », Woodhead, Cambridge, UK, 2012
- ❑ U. Ehrnsten, « Corrosion and stress corrosion cracking of austenitic stainless steels », chapter 5.05 in « Comprehensive Nuclear Materials, ed. R.J.M. Konings, Elsevier, 2012
- ❑ P.L. Andresen & G.S. Was, « Irradiation assisted stress corrosion cracking », chapter 5.08 in « Comprehensive Nuclear Materials, ed. R.J.M. Konings, Elsevier, 2012
- ❑ D. Féron & R. Staehle, "Stress corrosion cracking of nickel-based alloys in water-cooled nuclear reactors – the Coriou effect" , EFC N°67, Woodhead, Cambridge, UK, 2016.

