



Study of the hydrolysis of an industrial radio-oxidized poly(ester urethane)

E. Fromentin, J. Frey, S. Legand, J. J. Pielawski, P. E. Reiller, D. Doizi, C. Aymes-Chodur, S. Esnouf, M. Ferry

► To cite this version:

E. Fromentin, J. Frey, S. Legand, J. J. Pielawski, P. E. Reiller, et al.. Study of the hydrolysis of an industrial radio-oxidized poly(ester urethane). (IRaP) - The 12th meeting of the “Ionizing radiation and polymers” symposium 2016, Sep 2016, Porquerolles, France. hal-02442285

HAL Id: hal-02442285

<https://cea.hal.science/hal-02442285>

Submitted on 16 Jan 2020

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

STUDY OF THE HYDROLYSIS OF AN INDUSTRIAL RADIO- OXIDIZED POLY(ESTER URETHANE)

IRaP 2016, 25-30th September



Porquerolles Island, source: the Internet

E. Fromentin*, J. Frey, S. Legand, J.J. Pielawski,
P. E. Reiller, D. Doizi, C. Aymes-Chodur, S. Esnouf, M. Ferry


* elodie.fromentin@cea.fr

DE LA RECHERCHE À L'INDUSTRIE
cea den





Nuclear waste management

Several countries are considering a deep geological disposal.

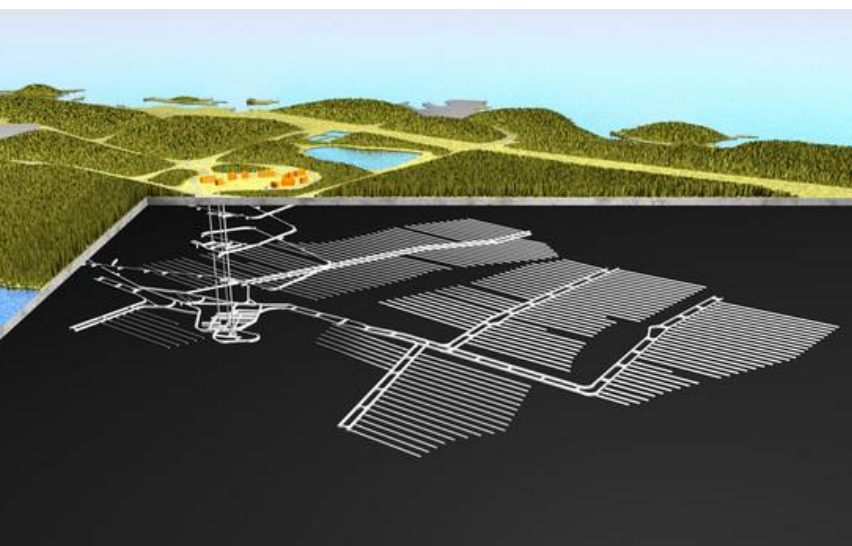


Finland, www.posiva.fi

Migmatic gneiss + bentonite clay, 400-450 meters depth

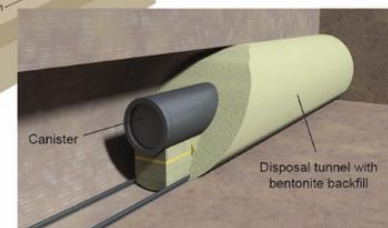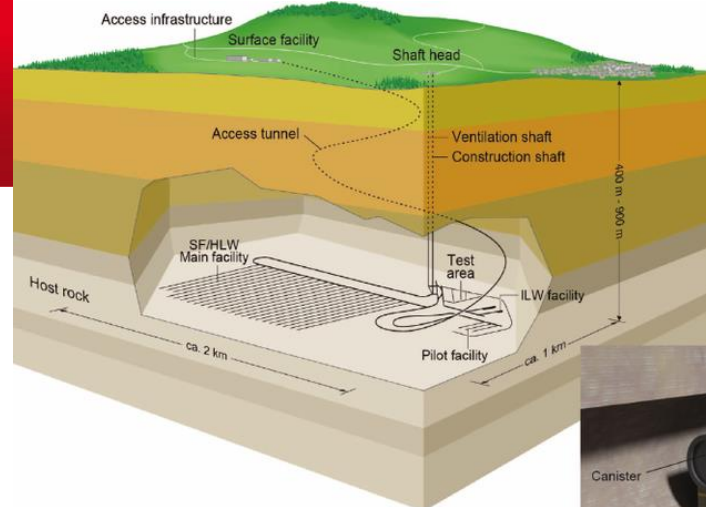

Switzerland, www.nagra.ch

Opanilus clay, 300-900 meters depth

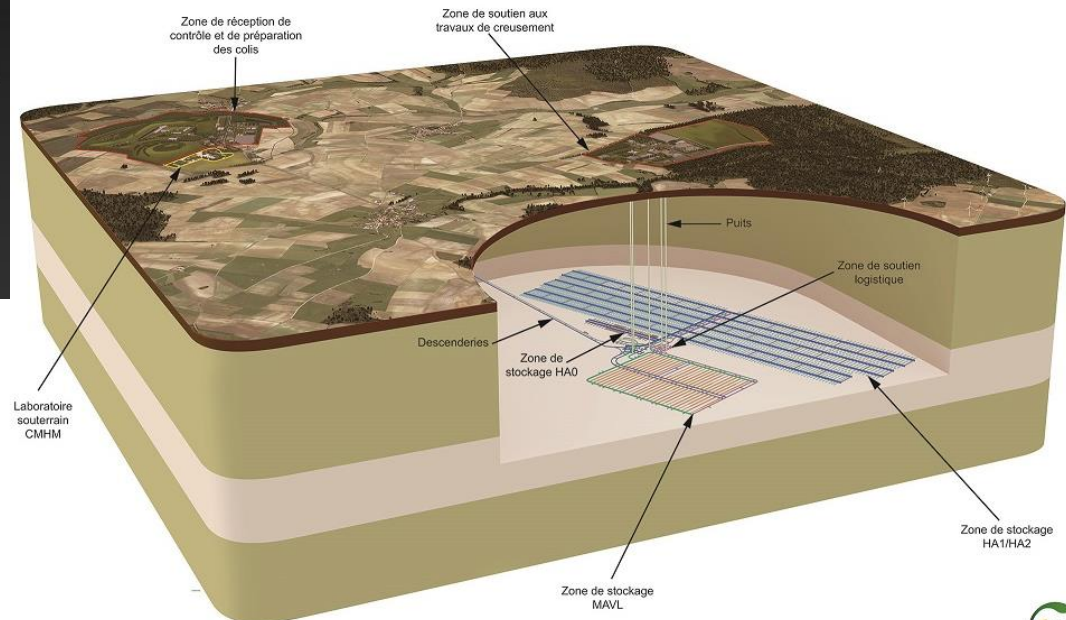

France, www.cigéo.com

Callovo-Oxfordian clay, 500 meters depth


Echelle des ouvrages non respectée.
Pendage des formations géologiques non représenté.

Polymers in nuclear waste packages

- Polyvinyl chloride, cellulose, ion-exchange resins, polyethylene...
- What will become polymers inside the geological disposal?




An example of an Intermediate Level Long-Lived waste package

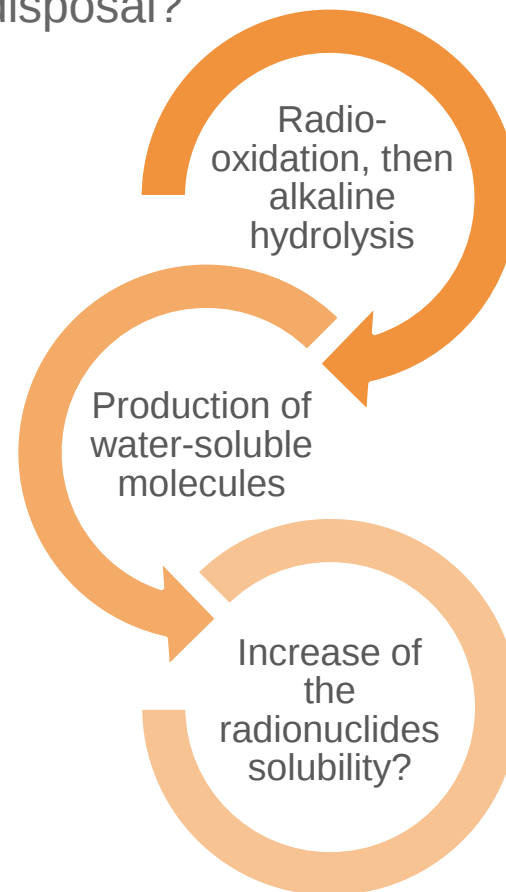


Considered polymer

- Poly(ester urethane) (PUR)
 - Constituent of gloves for glove boxes

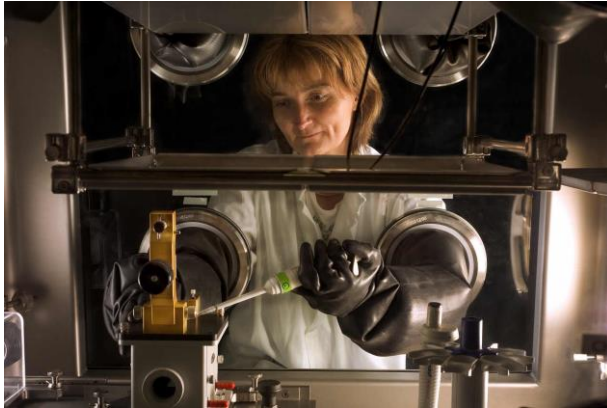


- Composed of 3 segments synthesized from these precursors:

hard segment

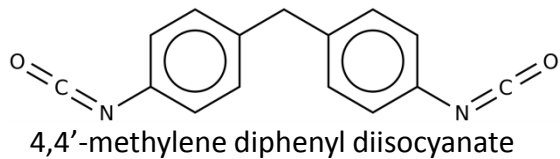


25.5%_w

extender



soft segment

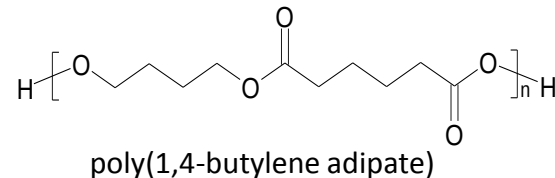63.4%_w

- + 8.9% inorganic fillers
- + 1,8% cross linking agents
- + 0,4% pigments

Objectives

- Characterizing and quantifying water-soluble molecules created by the alkaline hydrolysis of the non-irradiated and irradiated PUR at different doses
- Understanding the degradation mechanisms
 - PUR under radiolysis
 - Irradiated PUR under hydrolysis
- Identifying the products than can complex the radionuclides
- Being able to model the complexant release kinetics

Objectives

- Characterizing and quantifying water-soluble molecules created by the alkaline hydrolysis of the non-irradiated and irradiated PUR at different doses

- Understanding the degradation mechanisms
 - PUR under radiolysis
 - Irradiated PUR under hydrolysis

- Identifying the products than can complex the radionuclides



Being able to model the complexant release kinetics

MATERIALS: A TWO-STEP PREPARATION

■ **1st step:** PUR is irradiated under air using γ rays by LABRA (^{60}Co source), dose rate: $\sim 0.9 \text{ kGy.h}^{-1}$, doses: 500 kGy and 1,000 kGy

■ **2nd step:** non-irradiated and irradiated PUR are then hydrolyzed
3 temperature values: room temperature ($\approx 23^\circ\text{C}$), 40 and 60°C
 Δt is variable and depends on the degradation rate




MATERIALS: A TWO-STEP PREPARATION

- **1st step:** PUR is irradiated under air using γ rays by LABRA (^{60}Co source), dose rate: $\sim 0.9 \text{ kGy.h}^{-1}$, doses: 500 kGy and 1,000 kGy
- **2nd step:** non-irradiated and irradiated PUR are then hydrolyzed
3 temperature values: room temperature ($\sim 23^\circ\text{C}$), 40 and 60°C
 Δt is variable and depends on the degradation rate



Mass loss

- 3 temperatures, 3 doses
- Room temperature $\approx 23^{\circ}\text{C}$

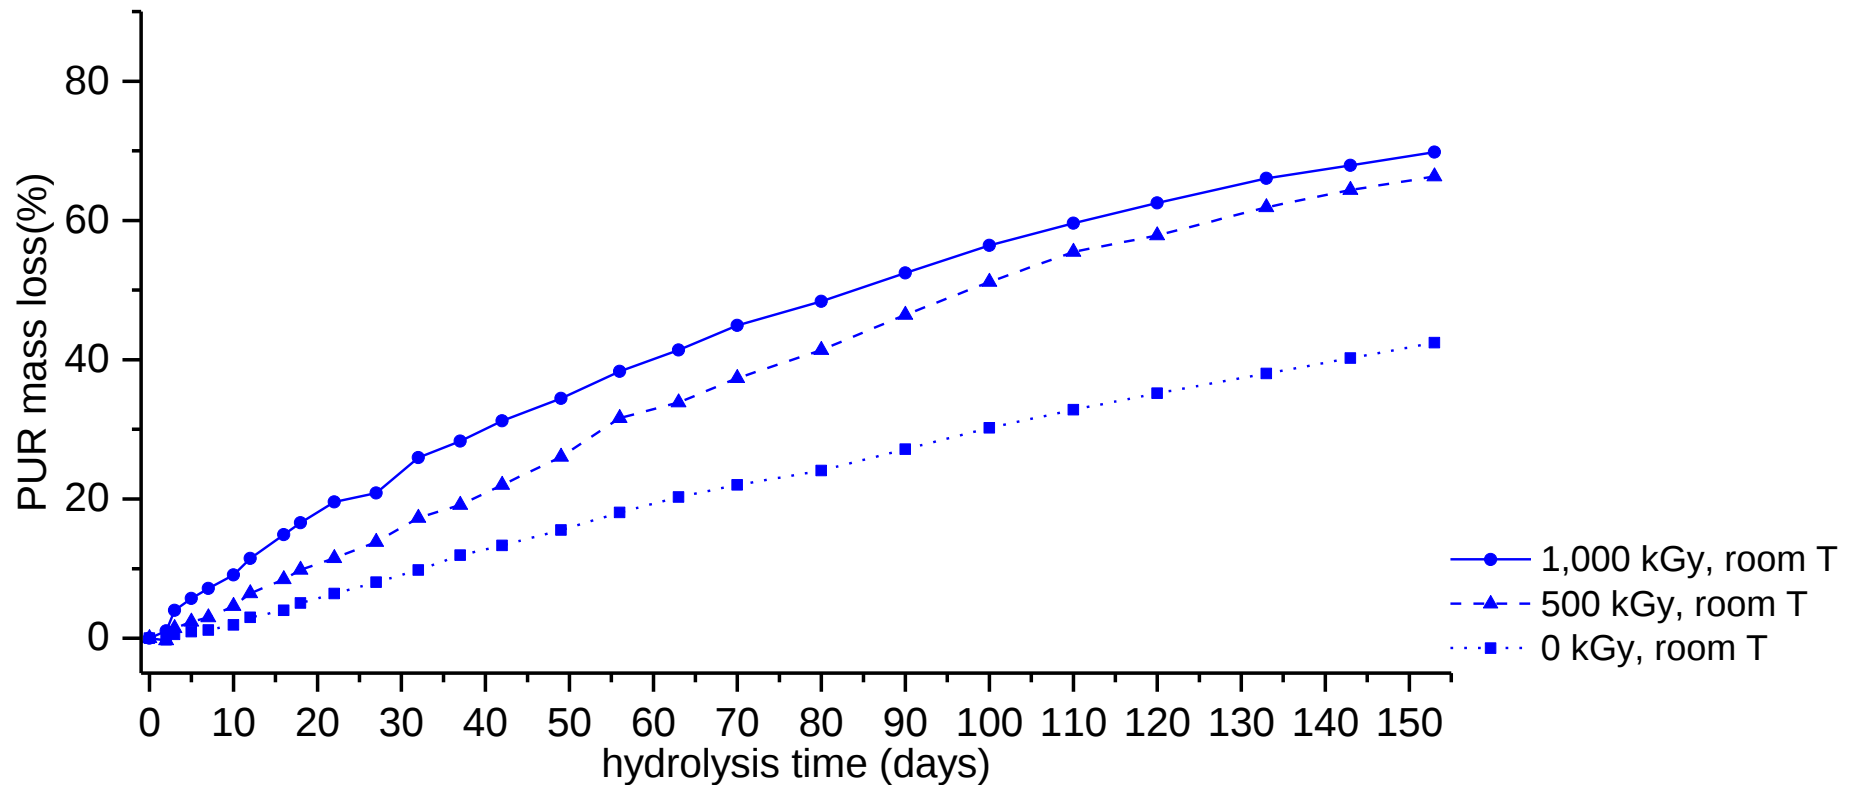


Mass loss

■ 3 temperatures, 3 doses


■ Room temperature $\approx 23^{\circ}\text{C}$

■ 40°C

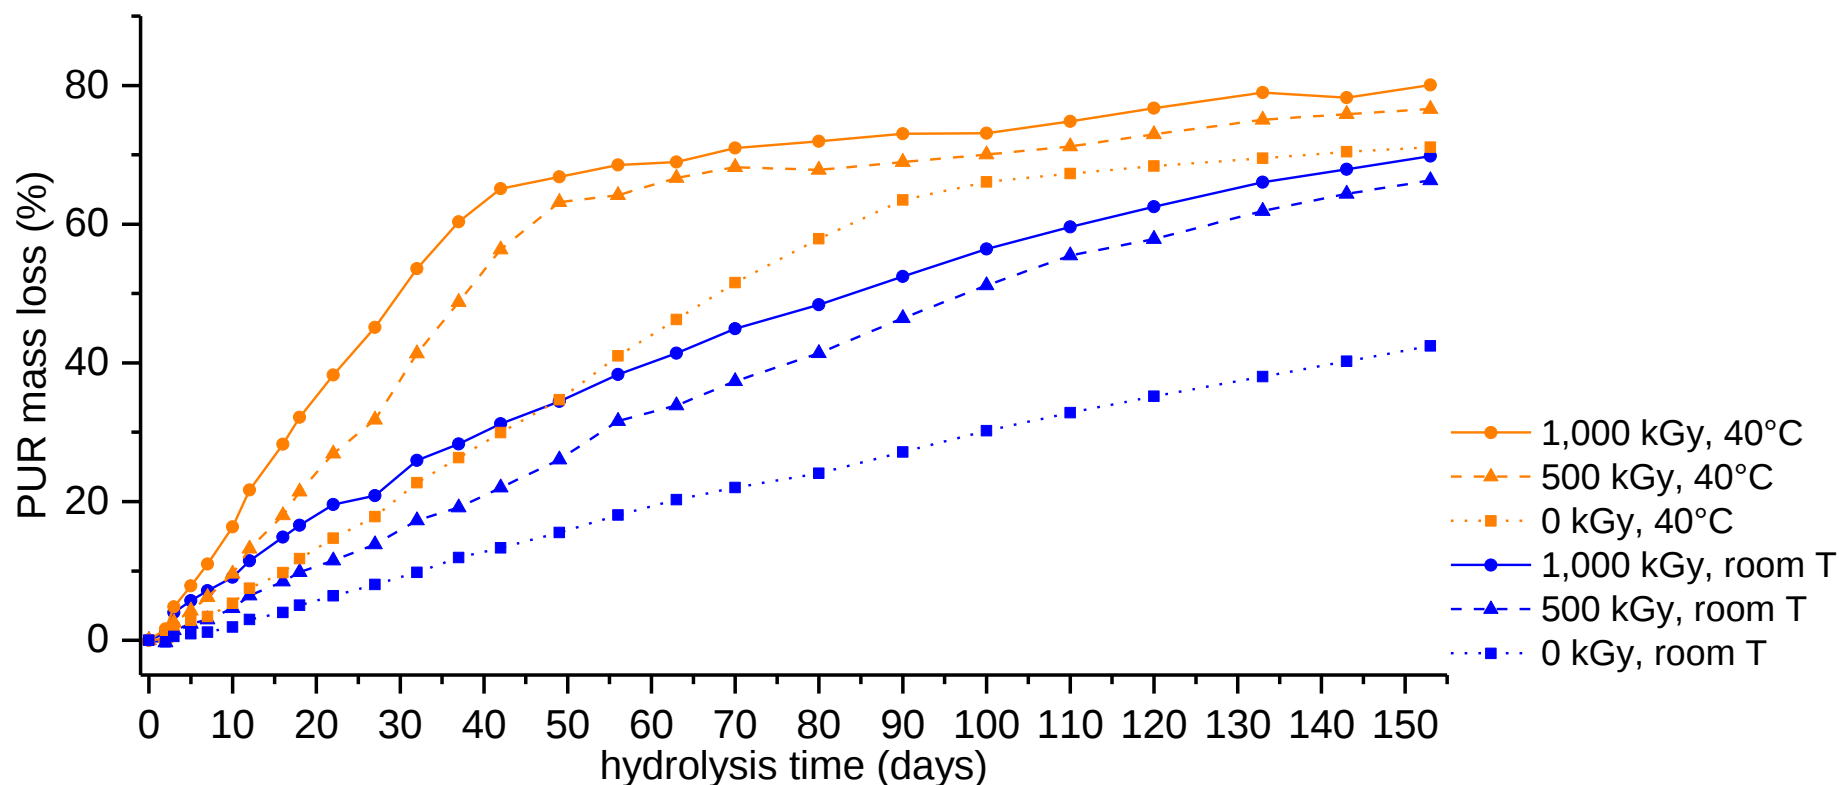

Mass loss


■ 3 temperatures, 3 doses

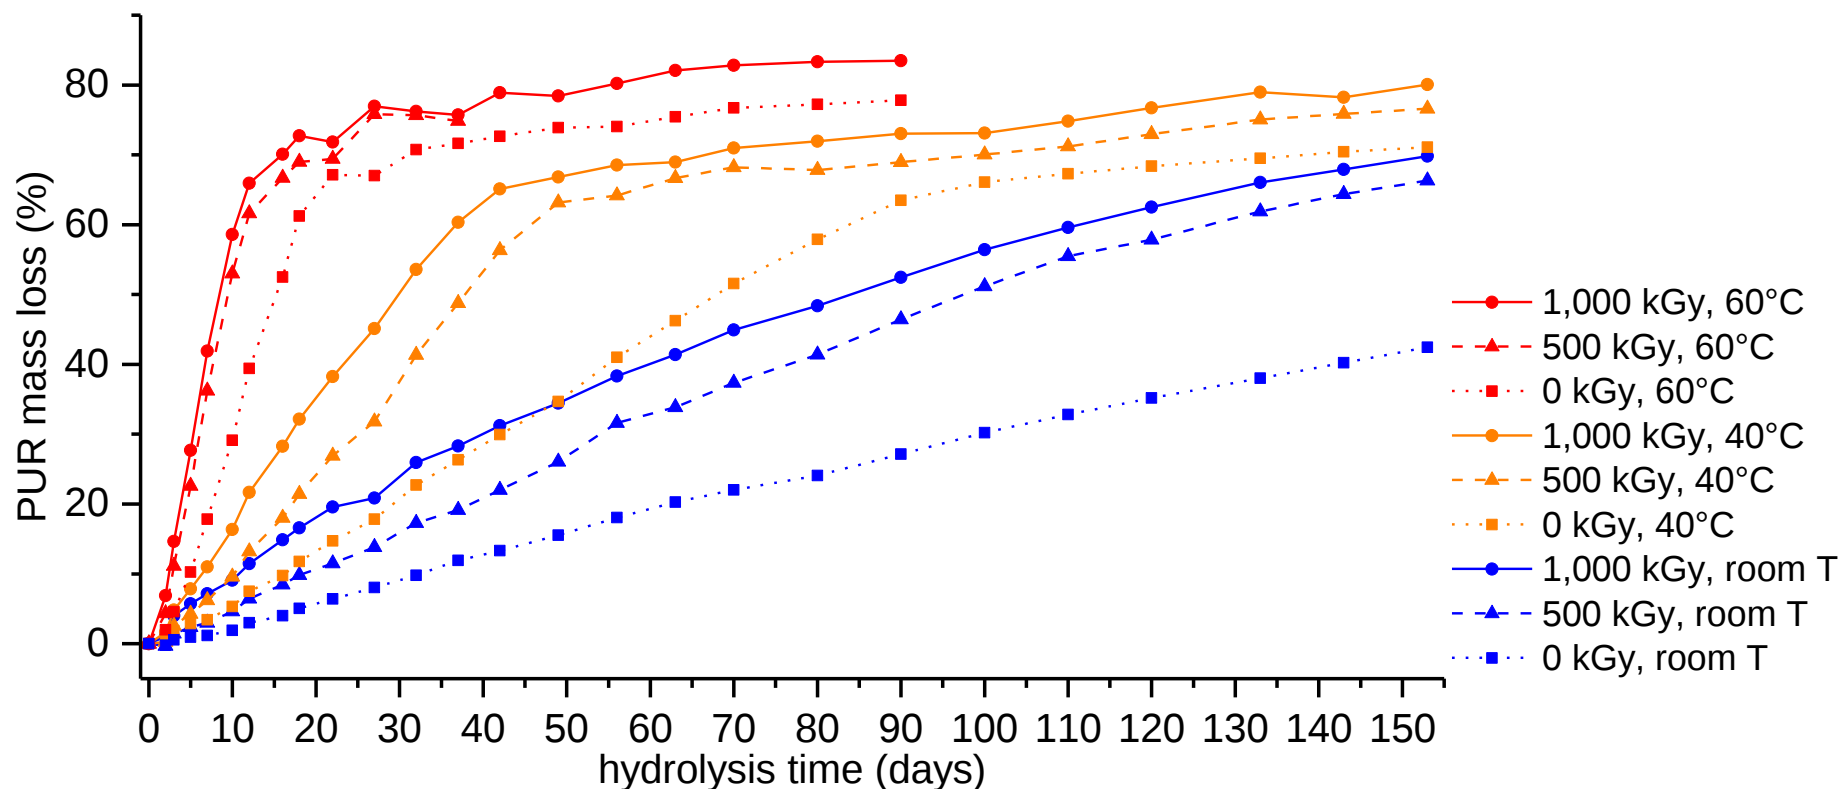■ Room temperature $\approx 23^{\circ}\text{C}$ ■ 40°C ■ 60°C 

Additional data


■ Error bar: $\sigma_{\max} = 4\%$

Measurements of the mass loss on the unirradiated PUR hydrolyzed at 60°C

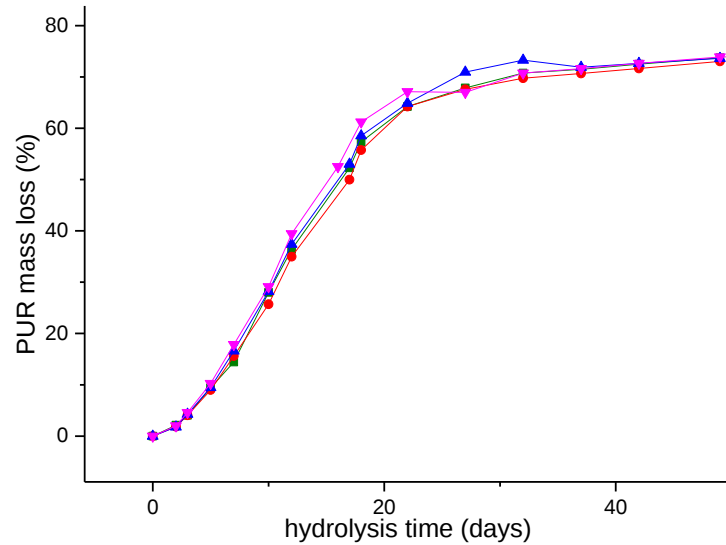

MATERIALS: A TWO-STEP PREPARATION


- **1st step:** PUR is irradiated under air using γ rays by LABRA (^{60}Co source), dose rate: $\sim 0.9 \text{ kGy.h}^{-1}$, doses: 500 kGy and 1,000 kGy
- **2nd step:** non-irradiated and irradiated PUR are then hydrolyzed
3 temperature values: room temperature ($\approx 23^\circ\text{C}$), 40 and 60°C
 Δt is variable and depends on the degradation rate

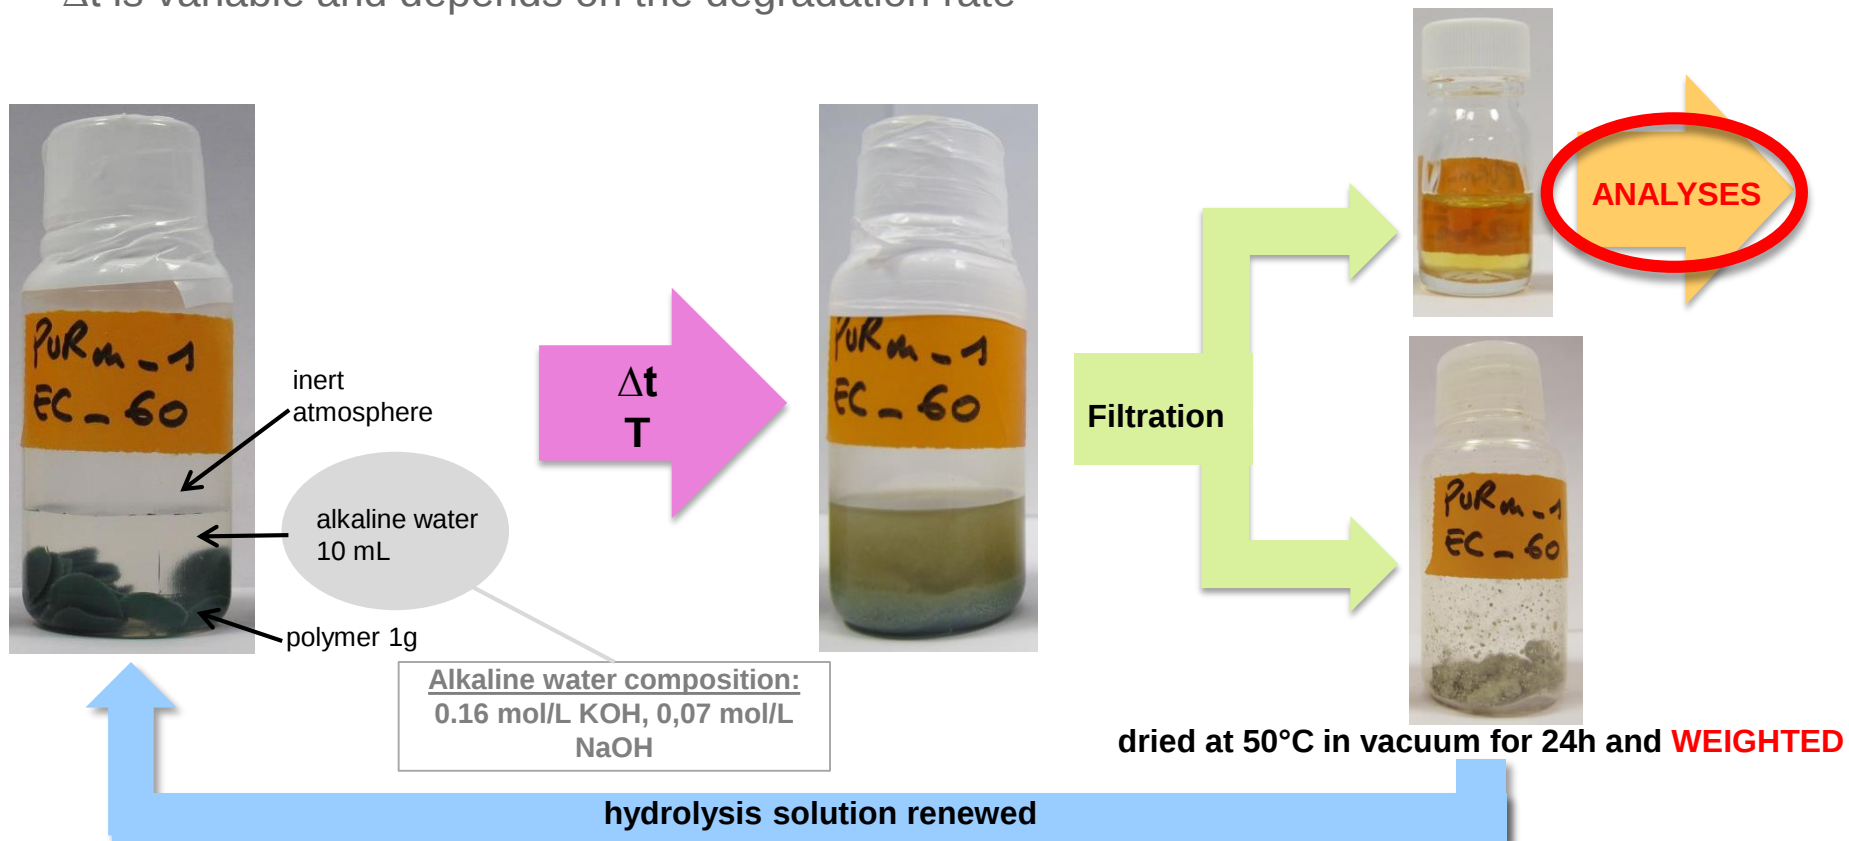



Additional data

■ Error bar: $\sigma_{\max} = 4\%$


Measurements of the mass loss on the unirradiated PUR hydrolyzed at 60°C

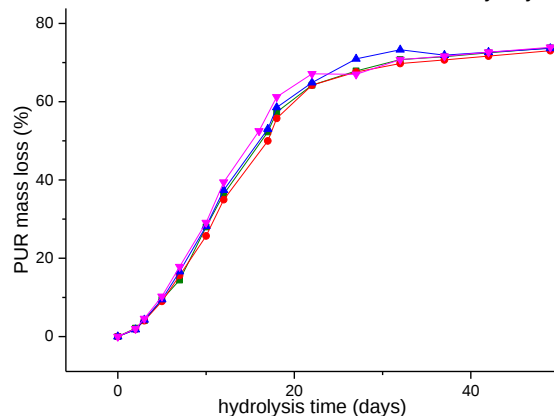

■ Total Organic Carbon = TOC is proportional to mass loss

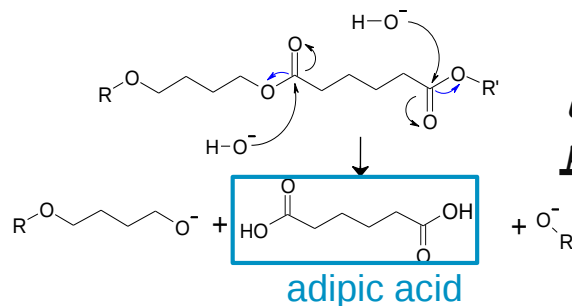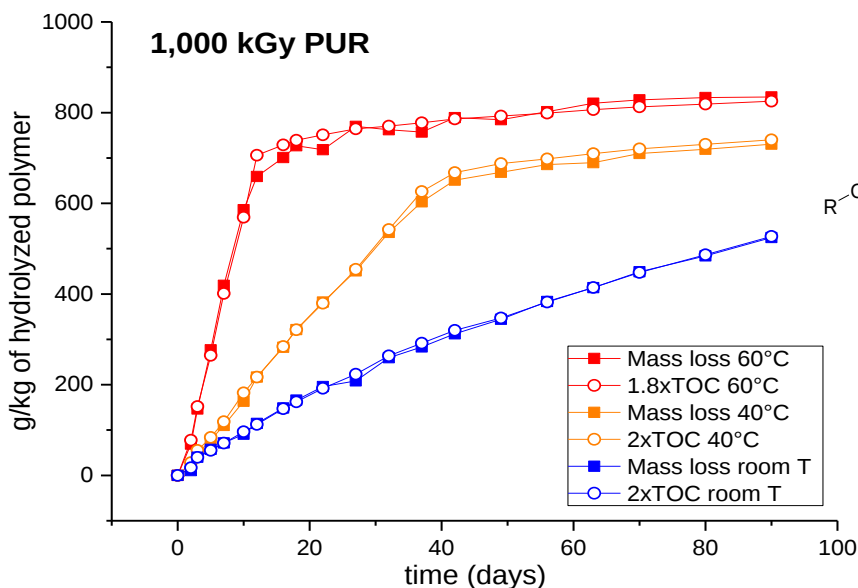

Mass balance of hydrolysis solution of 1,000 kGy PUR at day 31 at room T:

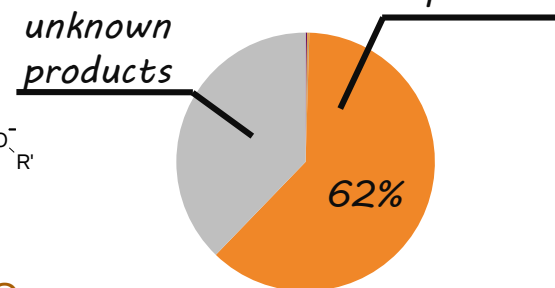

Degradation product $C_xH_yO_z$

$$\frac{\text{mass loss}}{\text{mass of carbon}} = \frac{xm_C + ym_H + zm_O}{xm_C} \approx 2$$


→ adipate $C_6H_8O_4$ corresponds

■ Yoon's model

■ Hypotheses:

- Hydrolysis of each chain occurs with equal probability.
- Water diffusion into the polymer does not limit hydrolysis.
- Water-soluble products are immediately leached out of the polymer.
- Hydrolysis is a complete reaction.

■ Involved reactions:

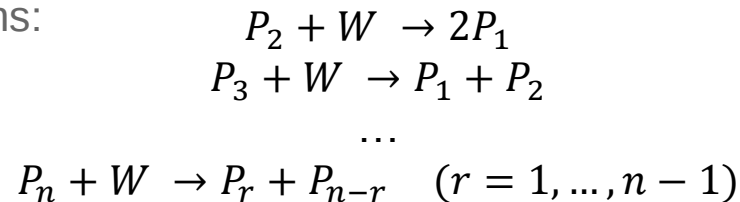

■ Induced rates:

$$\begin{aligned}
 \frac{d[P_1]}{dt} &= 2k_H[W] \sum_{i=2}^{\infty} [P_i] \\
 \frac{d[P_2]}{dt} &= -k_H[W][P_2] + 2k_H[W] \sum_{i=3}^{\infty} [P_i] \\
 &\dots \\
 \frac{d[P_n]}{dt} &= -(n-1)k_H[W][P_n] + 2k_H[W] \sum_{i=n+1}^{\infty} [P_i]
 \end{aligned}$$

■ Yoon's model

■ After mathematical geniuses work:

$$\begin{aligned}\frac{[P_1]}{\lambda_1} &= 1 - 2\left(1 - \frac{1}{\mu_{n0}}\right)e^{-\tau} + \left(1 - \frac{2}{\mu_{n0}}\right)e^{-2\tau} \\ \frac{[P_2]}{\lambda_1} &= \left(1 - \frac{1}{\mu_{n0}}\right)e^{-\tau} - 2\left(1 - \frac{2}{\mu_{n0}}\right)e^{-2\tau} + \left(1 - \frac{3}{\mu_{n0}}\right)e^{-3\tau} \\ &\quad \dots \\ \frac{[P_k]}{\lambda_1} &= \left(1 - \frac{(k-1)}{\mu_{n0}}\right)e^{-(k-1)\tau} - 2\left(1 - \frac{k}{\mu_{n0}}\right)e^{-k\tau} + \left(1 - \frac{(k+1)}{\mu_{n0}}\right)e^{-(k+1)\tau}\end{aligned}$$

with $\lambda_k = \sum_{n=1}^{\infty} n^k [P_n]$, $\tau = \int_0^t k_H [W] dt$, $\mu_{n0} = \frac{\sum_{i=1}^{\infty} i [P_i]}{\sum_{i=1}^{\infty} [P_i]} = \frac{\lambda_1}{\lambda_0}$


■ Considering that μ_{n0} is very high and that only P_1 is water-soluble:

$$[P_1] \approx \lambda_1 (1 - 2e^{-k_H t} + e^{-2k_H t})$$

■ Yoon's model applied to our experimental data

■ 40 and 60°C → the model matches

$$[P_1] \approx \lambda_1(1 - 2e^{-k_H t} + e^{-2k_H t})$$

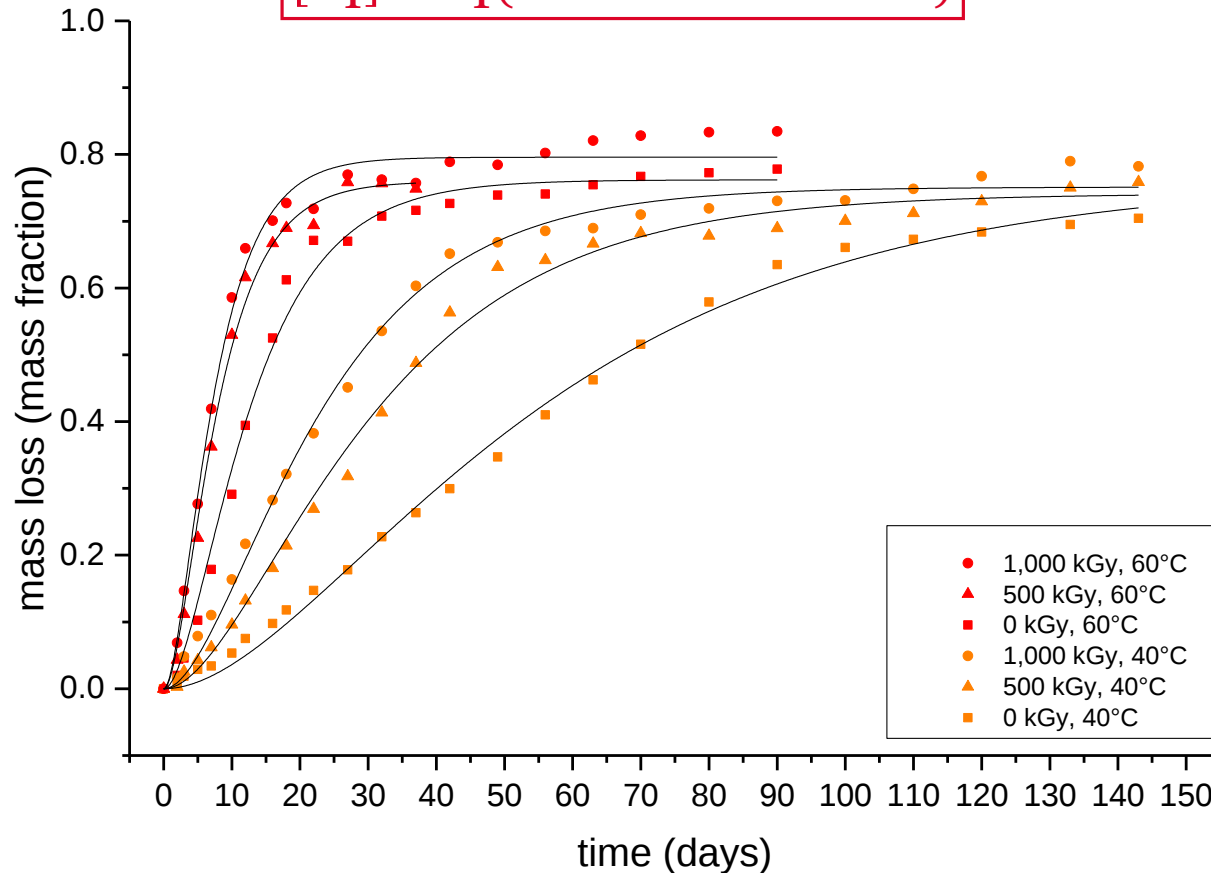


$$k_H = A \times e^{-\frac{E_a}{RT}}$$

Dose (kGy)	Activation energy between 40 et 60°C (kJ.mol ⁻¹)
0	64
500	59
1,000	49

■ Yoon's model applied to our experimental data


■ Room temperature → the model does not match...

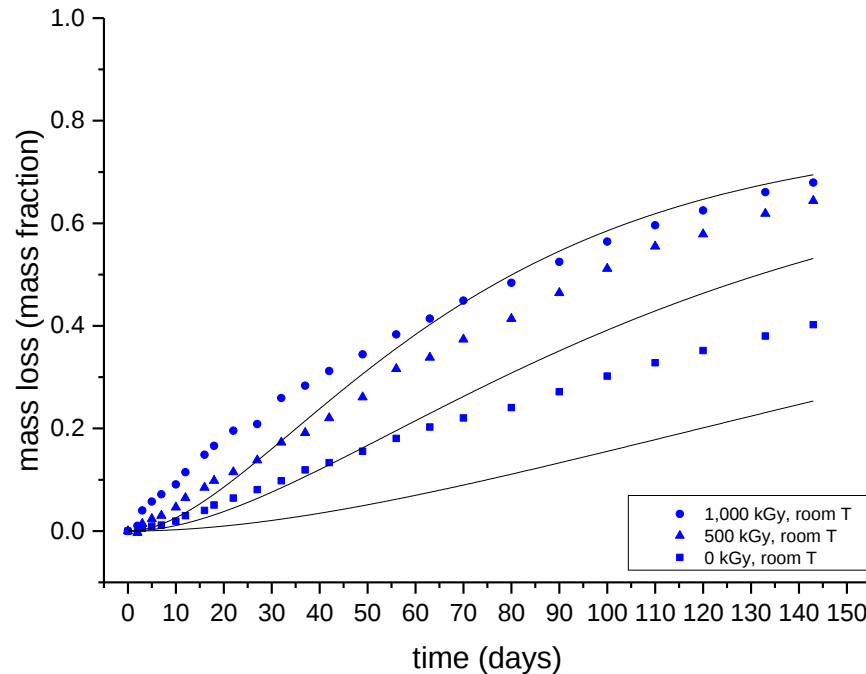

→ **Temperature affects the way** water-soluble products are released.

→ It is observed at **all doses**.

■ Time-temperature superposition approach

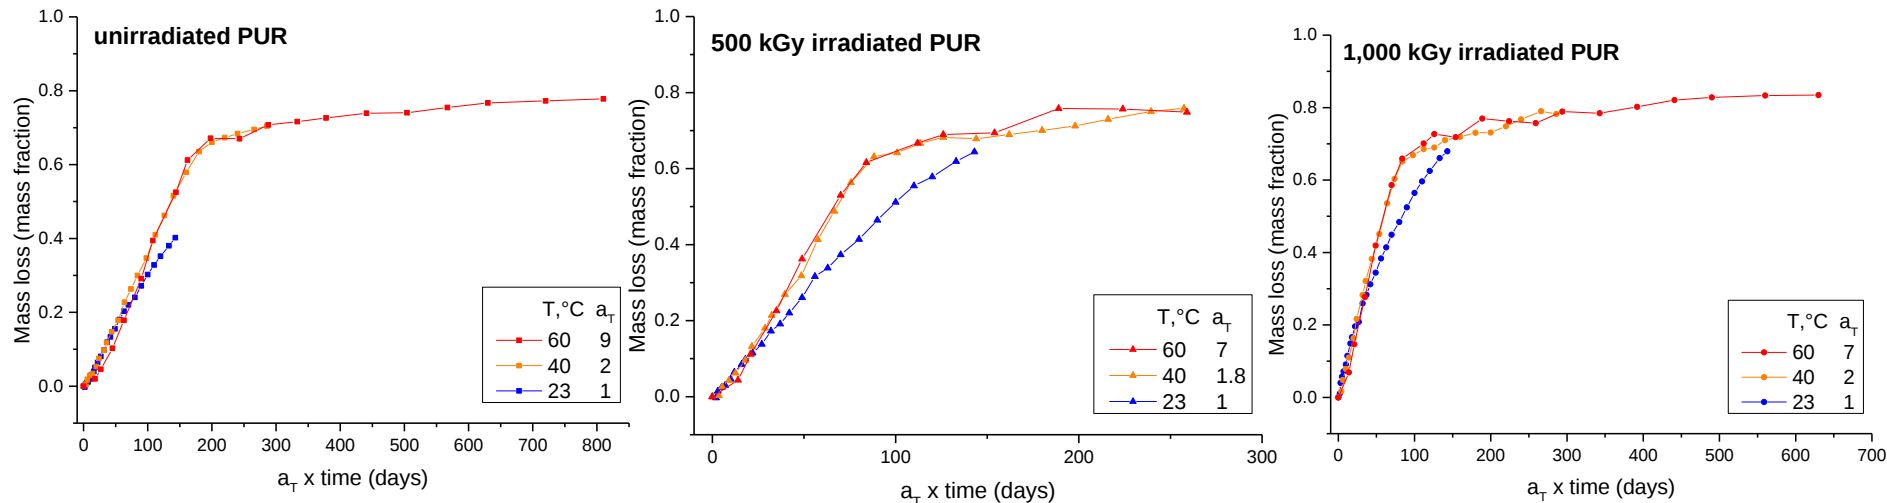

Data at room temperature cannot be overlaid by data at 40 and 60°C.

→ it confirms that **the release** of water-soluble products **is different** at room temperature.

HYPOTHESES FOR THIS DISCREPANCY

- Discrepancy: the degradation at room temperature is **faster** than expected. Something **speeds up** the reaction **or** the process is **different** at this temperature value.
- Hypotheses for this discrepancy:
 - Some of the Yoon's model hypotheses are not valid:
 - Reaction on surface (versus bulk reaction).
 - Water concentration inside the PUR depends on temperature.
 - There are two competing processes (hydrolysis is the predominant process at " high " temperature):
 - Plasticizing by water : PUR more porous.
 - Remained synthesis reactants and additives leaching at the first steps of the degradation.
 - Autocatalysis by degradation products i.e. adipic acid.*



* Salazar et al. (2003) *Journal of Polymer Science: Part A: Polymer Chemistry*, **41**, 1136-1151.

- Unirradiated, 500 and 1,000 kGy irradiated PUR hydrolyzed at room temperature ($\approx 23^{\circ}\text{C}$), 40 and 60°C :
 - Mass loss and Total Organic Carbon (TOC) show the same evolution.
 - The ratio between mass loss and TOC confirms that adipic acid is the main product.
- Whatever the dose, the release of soluble fraction at 40 and 60°C follows Yoon's model which means that the ester groups mainly hydrolyzed with equal probability and diffusion does not limit hydrolysis.
- The release of soluble fraction at 23°C does not follow Yoon's model. Several hypotheses to explain this discrepancy: autocatalysis? Plasticizing? Change in water concentration?
- Perspectives: improving the Yoon's model to cover the largest range of temperature.

=> Better understanding of the PUR hydrolysis kinetics. Next step: identifying the degradation products that can complex the radionuclides.

Thank you for your attention.

ACKNOWLEDGMENT

This work has been financed by CEA, AREVA NC, EDF. The authors are grateful to Florence Cochin for her scientific collaboration.

Thanks to V. Dauvois, Y. Ngono-Ravache E. Zekri, M. Tabarant, J.L. Roujou, D. Durand for their ideas and technical help.

Any questions?



More details on this subject :

Fromentin et al. (2016) *Polymer Degradation and Stability*, **128**, 172-181

Commissariat à l'énergie atomique et aux énergies alternatives
Centre de Saclay | 91191 Gif-sur-Yvette Cedex
T. +33 1 69 08 27 62 | elodie.fromentin@cea.fr

Etablissement public à caractère industriel et commercial | R.C.S Paris B 775 685 019

